

Report No.	20210393	Date of Receipt	2021-06-14	Date of test	2021-06-16 ~ 2021-06-25	
Client	SANGBO			Name	MinKyu Hwang	
Address	(10016) Tongjin-Eup Daeseomyeong-Ro 50, Gimpo, GyeongGi-DO, South Korea 10016			Uses	Quality Control	
Test Sample	SCHUTZEN CX60 (VLT 30%)		Test Item	Optical Properties		

Page(1)/(2)pages


Test Results

1. Test method used : ISO 9050:2003, 3.2 Performance of optical measurements
KS L 2016:2014, 6.3 Performance of optical measurements; JIS A 5759:2016, 6. Measurement method
KS L 2514:2011, 4. Measurement of spectral transmission and reflection factor
2. Instrument : 1) FT-IR, Spectrophotometer, Nicolet, 6700, U.S.A.
2) UV-VIS-NIR Spectrophotometer, Perkin-Elmer, Lambda 950 & 1050, U.S.A.
3. Testing environment : Temperature :min 21 °C,max 25 °C, Humidity :min 60 % R.H.,max 65 % R.H.
4. Test Results :

Test Item	Symbol	Unit	ISO 9050 :2003	KS L 2016 :2014	JIS A 5759 :2016	KS L 2514 :2011
Solar Energy Transmittance	TE	%	25.2	26.3	25.2	25.2
Visible Light Transmittance	TL	%	29.9	29.7	29.9	29.9
Ultra Violet Transmittance	TUV	%	0.2		0.2	0.2
Solar Energy Reflectance(Ext.)	RE(e)	%	5.1	5.1	5.1	5.1
Solar Energy Reflectance(Int.)	RE(i)	%	5.5	5.6	5.5	5.4
Visible Light Reflectance(Ext.)	RL(e)	%	5.4	5.4	5.4	5.4
Visible Light Reflectance(Int.)	RL(i)	%	5.9	5.8	5.9	5.9
Solar Energy Absorbance(Ext.)	AE(e)	%	69.7	68.6	69.7	69.8
Correct Emissivity(Ext.)	E(e)	-				0.84
Correct Emissivity(Int.)	E(i)	-				0.87
Shading Coefficient	SC	-		0.57	0.56	
U-Value (Winter)	U-Value	W/m ² K		6.0	6.0	
Solar Heat Gain Coefficient	SHGC	-			0.49	0.49
Solar Factor	S Factor	%	43.5			

* Measuring condition(TL% & RL%) : ISO 9050, JIS A 5759 & KS L 2514 : D65/2, KS L 2016 : A/2

** Measuring condition(TE%,RE% & TUV%) : AM=1.5(300nm~2500nm), Film side (attached 3mm Clear Glass) : Inside
' Continued '

Affirmation	Measurements performed by Name : Kim, Shin Ae 	Approved by Title : Technical Manager Name : Park, Dong Young 
-------------	--	---

28 - 06 - 2021

Hankuk Glass Industries Inc.
Director of R&D Center
Accredited by KOLAS, Republic of KOREA



1. The results shown in this test report refer only to the sample(s) tested unless otherwise stated.
2. The above test report can not be used for any advertisement & lawsuit and for other purpose than submitted.
3. The above test certificate is the accredited test result by Korea Laboratory Accreditation Scheme, which signed the ILAC-MRA.

4. Test Results (Continued) :

Test Item	Unit	ISO 9050 :2003	KS L 2514 :2011
* Total Solar Energy Rejected (TSER)	%	56.5	50.6

* Film side(attached 3mm Clear Glass): Inside

* This laboratory is not accredited for the test results marked *.

Test Item	Unit	Spectrum average	Factor Application			
			ISO 9050 :2003	KS L 2016 :2014	JIS A 5759 :2016	KS L 2514 :2011
** Transmittance (780 nm ~ 2 500 nm)	%	17.0	22.1	22.9	22.1	21.9


** Film side(attached 3mm Clear Glass): Inside

** This laboratory is not accredited for the test results marked **.

5. Specification of Sample :

Sample Type	Film attached Glass	Adhesive Strength	Exist
Film Side (Outside -> Inside)	Side 2	Substrate	3 mm Clear Glass

6. Picture of Sample :

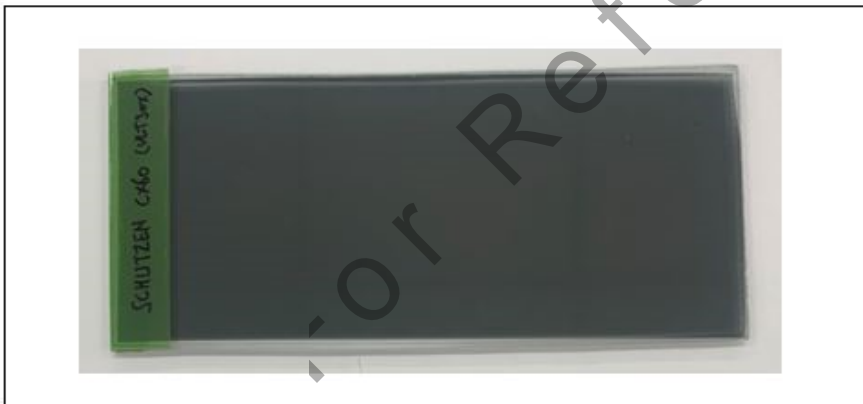

* The result is regarding the sample which is the 3mm clear glass attaching the film

' End '

Hankuk Glass Industries Inc., R&D Center
296, Oehang 1-gil, Gunsan-si, Jeollabuk-do, (54008), Korea TEL (063) 460-1333 FAX (063) 467-2985

Report No.	20210394	Date of Receipt	2021-06-14	Date of test	2021-06-16 ~ 2021-06-25
Client	SANGBO			Name	MinKyu Hwang
Address	(10016) Tongjin-Eup Daeseomyeong-Ro 50, Gimpo, GyeongGi-DO, South Korea 10016			Uses	Quality Control
Test Sample	SCHUTZEN CX90 (VLT 30%)		Test Item	Optical Properties	

Page(1)/(2)pages

Test Results

1. Test method used : ISO 9050:2003, 3.2 Performance of optical measurements
KS L 2016:2014, 6.3 Performance of optical measurements; JIS A 5759:2016, 6. Measurement method
KS L 2514:2011, 4. Measurement of spectral transmission and reflection factor
2. Instrument : 1) FT-IR, Spectrophotometer, Nicolet, 6700, U.S.A.
2) UV-VIS-NIR Spectrophotometer, Perkin-Elmer, Lambda 950 & 1050, U.S.A.
3. Testing environment : Temperature :min 21 °C,max 25 °C, Humidity :min 60 % R.H.,max 65 % R.H.
4. Test Results :

Test Item	Symbol	Unit	ISO 9050 :2003	KS L 2016 :2014	JIS A 5759 :2016	KS L 2514 :2011
Solar Energy Transmittance	TE	%	16.8	17.5	16.8	15.5
Visible Light Transmittance	TL	%	31.5	31.2	31.5	31.5
Ultra Violet Transmittance	TUV	%	0.3		0.3	0.3
Solar Energy Reflectance(Ext.)	RE(e)	%	5.0	5.0	5.0	4.9
Solar Energy Reflectance(Int.)	RE(i)	%	5.4	5.0	5.4	5.3
Visible Light Reflectance(Ext.)	RL(e)	%	5.5	5.5	5.5	5.5
Visible Light Reflectance(Int.)	RL(i)	%	5.9	5.9	5.9	5.9
Solar Energy Absorbance(Ext.)	AE(e)	%	78.3	77.6	78.3	79.6
Correct Emissivity(Ext.)	E(e)	-				0.84
Correct Emissivity(Int.)	E(i)	-				0.87
Shading Coefficient	SC	-		0.50	0.50	
U-Value (Winter)	U-Value	W/m ² K		6.0	6.1	
Solar Heat Gain Coefficient	SHGC	-			0.44	0.43
Solar Factor	S Factor	%	37.3			

* Measuring condition(TL% & RL%) : ISO 9050, JIS A 5759 & KS L 2514 : D65/2, KS L 2016 : A/2

** Measuring condition(TE%,RE% & TUV%) : AM=1.5(300nm~2500nm), Film side (attached 3mm Clear Glass) : Inside
' Continued '

Affirmation	Measurements performed by Name : Kim, Shin Ae	Approved by Title : Technical Manager Name : Park, Dong Young
-------------	--	---

28 - 06 - 2021

Hankuk Glass Industries Inc.
Director of R&D Center
Accredited by KOLAS, Republic of KOREA



1. The results shown in this test report refer only to the sample(s) tested unless otherwise stated.
2. The above test report can not be used for any advertisement & lawsuit and for other purpose than submitted.
3. The above test certificate is the accredited test result by Korea Laboratory Accreditation Scheme, which signed the ILAC-MRA.

4. Test Results (Continued) :

Test Item	Unit	ISO 9050 :2003	KS L 2514 :2011
* Total Solar Energy Rejected (TSER)	%	62.7	56.8

* Film side(attached 3mm Clear Glass): Inside

* This laboratory is not accredited for the test results marked *.

Test Item	Unit	Spectrum average	Factor Application			
			ISO 9050 :2003	KS L 2016 :2014	JIS A 5759 :2016	KS L 2514 :2011
** Transmittance (780 nm ~ 2 500 nm)	%	1.8	3.5	3.6	3.5	3.4


** Film side(attached 3mm Clear Glass): Inside

** This laboratory is not accredited for the test results marked **.

5. Specification of Sample :

Sample Type	Film attached Glass	Adhesive Strength	Exist
Film Side (Outside -> Inside)	Side 2	Substrate	3 mm Clear Glass

6. Picture of Sample :

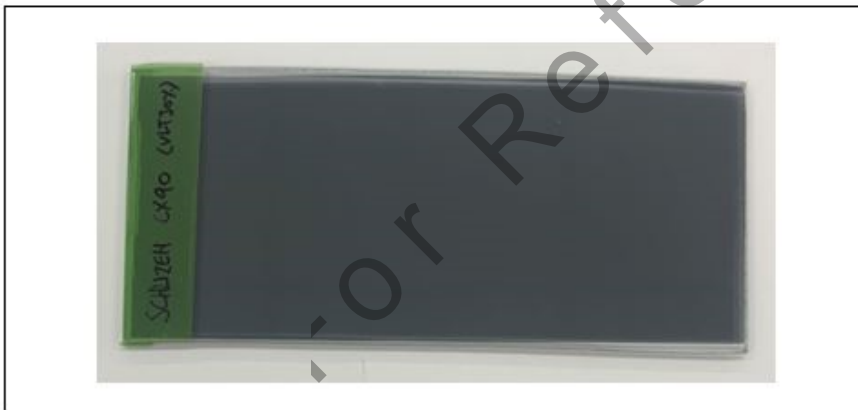

* The result is regarding the sample which is the 3mm clear glass attaching the film

' End '

Report No.	20210392	Date of Receipt	2021-06-14	Date of test	2021-06-16 ~ 2021-06-25	
Client	SANGBO			Name	MinKyu Hwang	
Address	(10016) Tongjin-Eup Daeseomyeong-Ro 50, Gimpo, GyeongGi-DO, South Korea 10016			Uses	Quality Control	
Test Sample	SCHUTZEN MX70 (VLT 27%)		Test Item	Optical Properties		

Page(1)/(2)pages

Test Results

1. Test method used : ISO 9050:2003, 3.2 Performance of optical measurements
KS L 2016:2014, 6.3 Performance of optical measurements; JIS A 5759:2016, 6. Measurement method
KS L 2514:2011, 4. Measurement of spectral transmission and reflection factor
2. Instrument : 1) FT-IR, Spectrophotometer, Nicolet, 6700, U.S.A.
2) UV-VIS-NIR Spectrophotometer, Perkin-Elmer, Lambda 950 & 1050, U.S.A.
3. Testing environment : Temperature :min 21 °C,max 25 °C, Humidity :min 60 % R.H.,max 65 % R.H.
4. Test Results :

Test Item	Symbol	Unit	ISO 9050 :2003	KS L 2016 :2014	JIS A 5759 :2016	KS L 2514 :2011
Solar Energy Transmittance	TE	%	24.1	25.2	24.1	24.2
Visible Light Transmittance	TL	%	27.1	26.2	27.1	27.1
Ultra Violet Transmittance	TUV	%	0.2		0.2	0.2
Solar Energy Reflectance(Ext.)	RE(e)	%	13.3	13.3	13.3	13.5
Solar Energy Reflectance(Int.)	RE(i)	%	8.1	8.3	8.1	8.1
Visible Light Reflectance(Ext.)	RL(e)	%	13.7	13.5	13.7	13.7
Visible Light Reflectance(Int.)	RL(i)	%	8.0	7.9	8.0	8.0
Solar Energy Absorbance(Ext.)	AE(e)	%	62.6	61.6	62.6	62.3
Correct Emissivity(Ext.)	E(e)	-				0.84
Correct Emissivity(Int.)	E(i)	-				0.83
Shading Coefficient	SC	-		0.52	0.52	
U-Value (Winter)	U-Value	W/m ² K		5.9	5.9	
Solar Heat Gain Coefficient	SHGC	-			0.45	0.45
Solar Factor	S Factor	%	40.2			

* Measuring condition(TL% & RL%) : ISO 9050, JIS A 5759 & KS L 2514 : D65/2, KS L 2016 : A/2

** Measuring condition(TE%,RE% & TUV%) : AM=1.5(300nm~2500nm), Film side (attached 3mm Clear Glass) : Inside
' Continued '

Affirmation	Measurements performed by Name : Kim, Shin Ae 	Approved by Title : Technical Manager Name : Park, Dong Young 
-------------	--	---

28 - 06 - 2021

Hankuk Glass Industries Inc.
Director of R&D Center
Accredited by KOLAS, Republic of KOREA



1. The results shown in this test report refer only to the sample(s) tested unless otherwise stated.
2. The above test report can not be used for any advertisement & lawsuit and for other purpose than submitted.
3. The above test certificate is the accredited test result by Korea Laboratory Accreditation Scheme, which signed the ILAC-MRA.

4. Test Results (Continued) :

Test Item	Unit	ISO 9050 :2003	KS L 2514 :2011
* Total Solar Energy Rejected (TSER)	%	59.8	54.6

* Film side(attached 3mm Clear Glass): Inside

* This laboratory is not accredited for the test results marked *.

Test Item	Unit	Spectrum average	Factor Application			
			ISO 9050 :2003	KS L 2016 :2014	JIS A 5759 :2016	KS L 2514 :2011
** Transmittance (780 nm ~ 2 500 nm)	%	16.9	23.4	24.8	23.4	23.3

** Film side(attached 3mm Clear Glass): Inside

** This laboratory is not accredited for the test results marked **.

5. Specification of Sample :

Sample Type	Film attached Glass	Adhesive Strength	Exist
Film Side (Outside -> Inside)	Side 2	Substrate	3 mm Clear Glass

6. Picture of Sample :



* The result is regarding the sample which is the 3mm clear glass attaching the film

' End '

Report No.	20210395	Date of Receipt	2021-06-14	Date of test	2021-06-16 ~ 2021-06-25	
Client	SANGBO			Name	MinKyu Hwang	
Address	(10016) Tongjin-Eup Daeseomyeong-Ro 50, Gimpo, GyeongGi-DO, South Korea 10016			Uses	Quality Control	
Test Sample	SCHUTZEN GX80 (VLT 27%)		Test Item	Optical Properties		

Page(1)/(2)pages

Test Results

1. Test method used : ISO 9050:2003, 3.2 Performance of optical measurements
KS L 2016:2014, 6.3 Performance of optical measurements; JIS A 5759:2016, 6. Measurement method
KS L 2514:2011, 4. Measurement of spectral transmission and reflection factor
2. Instrument : 1) FT-IR, Spectrophotometer, Nicolet, 6700, U.S.A.
2) UV-VIS-NIR Spectrophotometer, Perkin-Elmer, Lambda 950 & 1050, U.S.A.
3. Testing environment : Temperature :min 21 °C,max 25 °C, Humidity :min 60 % R.H.,max 65 % R.H.
4. Test Results :

Test Item	Symbol	Unit	ISO 9050 :2003	KS L 2016 :2014	JIS A 5759 :2016	KS L 2514 :2011
Solar Energy Transmittance	TE	%	21.8	22.7	21.8	21.6
Visible Light Transmittance	TL	%	27.6	27.3	27.6	27.6
Ultra Violet Transmittance	TUV	%	0.2		0.2	0.2
Solar Energy Reflectance(Ext.)	RE(e)	%	11.1	11.2	11.1	11.2
Solar Energy Reflectance(Int.)	RE(i)	%	8.3	8.3	8.3	8.2
Visible Light Reflectance(Ext.)	RL(e)	%	12.0	11.9	12.0	12.0
Visible Light Reflectance(Int.)	RL(i)	%	9.3	9.2	9.3	9.3
Solar Energy Absorbance(Ext.)	AE(e)	%	67.0	66.0	67.0	67.2
Correct Emissivity(Ext.)	E(e)	-				0.84
Correct Emissivity(Int.)	E(i)	-				0.86
Shading Coefficient	SC	-		0.52	0.51	
U-Value (Winter)	U-Value	W/m ² K		5.9	6.0	
Solar Heat Gain Coefficient	SHGC	-			0.45	0.45
Solar Factor	S Factor	%	39.3			

* Measuring condition(TL% & RL%) : ISO 9050, JIS A 5759 & KS L 2514 : D65/2, KS L 2016 : A/2

** Measuring condition(TE%,RE% & TUV%) : AM=1.5(300nm~2500nm), Film side (attached 3mm Clear Glass) : Inside
' Continued '

Affirmation	Measurements performed by Name : Kim, Shin Ae 	Approved by Title : Technical Manager Name : Park, Dong Young 
-------------	--	---

28 - 06 - 2021

Hankuk Glass Industries Inc.
Director of R&D Center
Accredited by KOLAS, Republic of KOREA



1. The results shown in this test report refer only to the sample(s) tested unless otherwise stated.
2. The above test report can not be used for any advertisement & lawsuit and for other purpose than submitted.
3. The above test certificate is the accredited test result by Korea Laboratory Accreditation Scheme, which signed the ILAC-MRA.

4. Test Results (Continued) :

Test Item	Unit	ISO 9050 :2003	KS L 2514 :2011
* Total Solar Energy Rejected (TSER)	%	60.7	55.2

* Film side(attached 3mm Clear Glass): Inside

* This laboratory is not accredited for the test results marked *.

Test Item	Unit	Spectrum average	Factor Application			
			ISO 9050 :2003	KS L 2016 :2014	JIS A 5759 :2016	KS L 2514 :2011
** Transmittance (780 nm ~ 2 500 nm)	%	13.1	17.9	18.6	17.9	17.7


** Film side(attached 3mm Clear Glass): Inside

** This laboratory is not accredited for the test results marked **.

5. Specification of Sample :

Sample Type	Film attached Glass	Adhesive Strength	Exist
Film Side (Outside -> Inside)	Side 2	Substrate	3 mm Clear Glass

6. Picture of Sample :

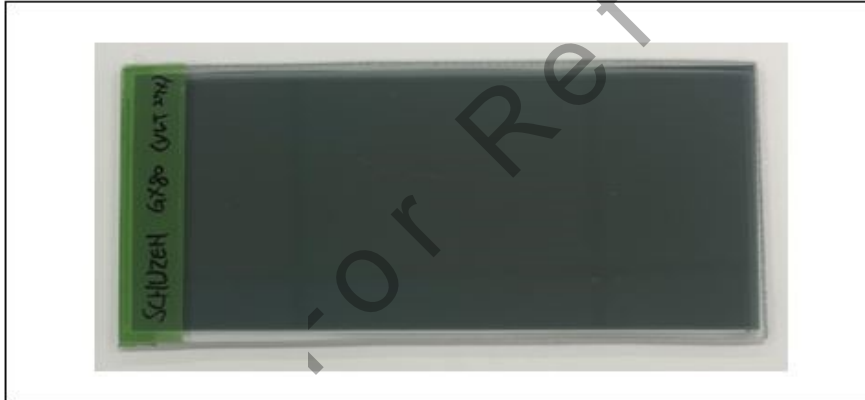

* The result is regarding the sample which is the 3mm clear glass attaching the film

' End '

Report No.	20210396	Date of Receipt	2021-06-14	Date of test	2021-06-16 ~ 2021-06-25	
Client	SANGBO			Name	MinKyu Hwang	
Address	(10016) Tongjin-Eup Daeseomyeong-Ro 50, Gimpo, GyeongGi-DO, South Korea 10016			Uses	Quality Control	
Test Sample	SCHUTZEN GX90 (VLT 27%)		Test Item	Optical Properties		

Page(1)/(2)pages

Test Results

1. Test method used : ISO 9050:2003, 3.2 Performance of optical measurements
KS L 2016:2014, 6.3 Performance of optical measurements; JIS A 5759:2016, 6. Measurement method
KS L 2514:2011, 4. Measurement of spectral transmission and reflection factor
2. Instrument : 1) FT-IR, Spectrophotometer, Nicolet, 6700, U.S.A.
2) UV-VIS-NIR Spectrophotometer, Perkin-Elmer, Lambda 950 & 1050, U.S.A.
3. Testing environment : Temperature :min 21 °C,max 25 °C, Humidity :min 60 % R.H.,max 65 % R.H.
4. Test Results :

Test Item	Symbol	Unit	ISO 9050 :2003	KS L 2016 :2014	JIS A 5759 :2016	KS L 2514 :2011
Solar Energy Transmittance	TE	%	15.6	16.2	15.6	14.5
Visible Light Transmittance	TL	%	28.5	28.0	28.5	28.5
Ultra Violet Transmittance	TUV	%	0.3		0.3	0.3
Solar Energy Reflectance(Ext.)	RE(e)	%	11.0	11.1	11.0	11.0
Solar Energy Reflectance(Int.)	RE(i)	%	7.1	6.8	7.1	6.8
Visible Light Reflectance(Ext.)	RL(e)	%	11.9	11.9	11.9	11.9
Visible Light Reflectance(Int.)	RL(i)	%	9.4	9.3	9.4	9.4
Solar Energy Absorbance(Ext.)	AE(e)	%	73.4	72.8	73.4	74.5
Correct Emissivity(Ext.)	E(e)	-				0.84
Correct Emissivity(Int.)	E(i)	-				0.86
Shading Coefficient	SC	-		0.47	0.47	
U-Value (Winter)	U-Value	W/m ² K		5.9	6.0	
Solar Heat Gain Coefficient	SHGC	-			0.41	0.40
Solar Factor	S Factor	%	34.8			

* Measuring condition(TL% & RL%) : ISO 9050, JIS A 5759 & KS L 2514 : D65/2, KS L 2016 : A/2

** Measuring condition(TE%,RE% & TUV%) : AM=1.5(300nm~2500nm), Film side (attached 3mm Clear Glass) : Inside
' Continued '

Affirmation	Measurements performed by Name : Kim, Shin Ae 	Approved by Title : Technical Manager Name : Park, Dong Young 
-------------	--	---

28 - 06 - 2021

Hankuk Glass Industries Inc.
Director of R&D Center
Accredited by KOLAS, Republic of KOREA



1. The results shown in this test report refer only to the sample(s) tested unless otherwise stated.
2. The above test report can not be used for any advertisement & lawsuit and for other purpose than submitted.
3. The above test certificate is the accredited test result by Korea Laboratory Accreditation Scheme, which signed the ILAC-MRA.

4. Test Results (Continued) :

Test Item	Unit	ISO 9050 :2003	KS L 2514 :2011
* Total Solar Energy Rejected (TSER)	%	65.2	59.8

* Film side(attached 3mm Clear Glass): Inside

* This laboratory is not accredited for the test results marked *.

Test Item	Unit	Spectrum average	Factor Application			
			ISO 9050 :2003	KS L 2016 :2014	JIS A 5759 :2016	KS L 2514 :2011
** Transmittance (780 nm ~ 2 500 nm)	%	2.4	4.2	4.4	4.2	4.1


** Film side(attached 3mm Clear Glass): Inside

** This laboratory is not accredited for the test results marked **.

5. Specification of Sample :

Sample Type	Film attached Glass	Adhesive Strength	Exist
Film Side (Outside -> Inside)	Side 2	Substrate	3 mm Clear Glass

6. Picture of Sample :

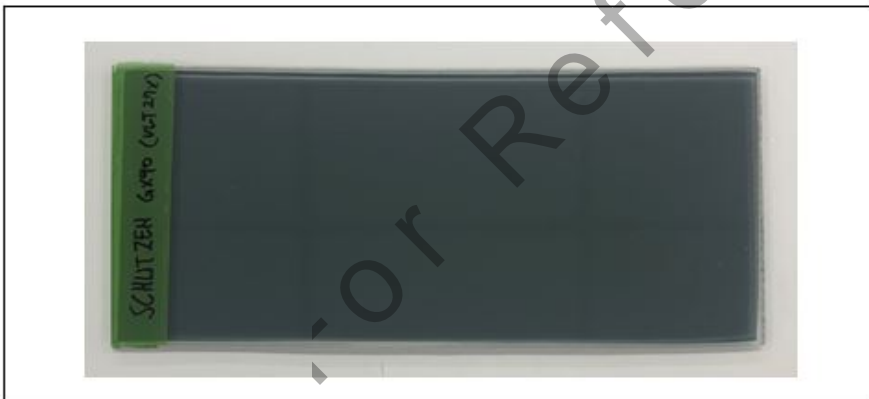

* The result is regarding the sample which is the 3mm clear glass attaching the film

' End '